



# 杭州科德磁业有限公司

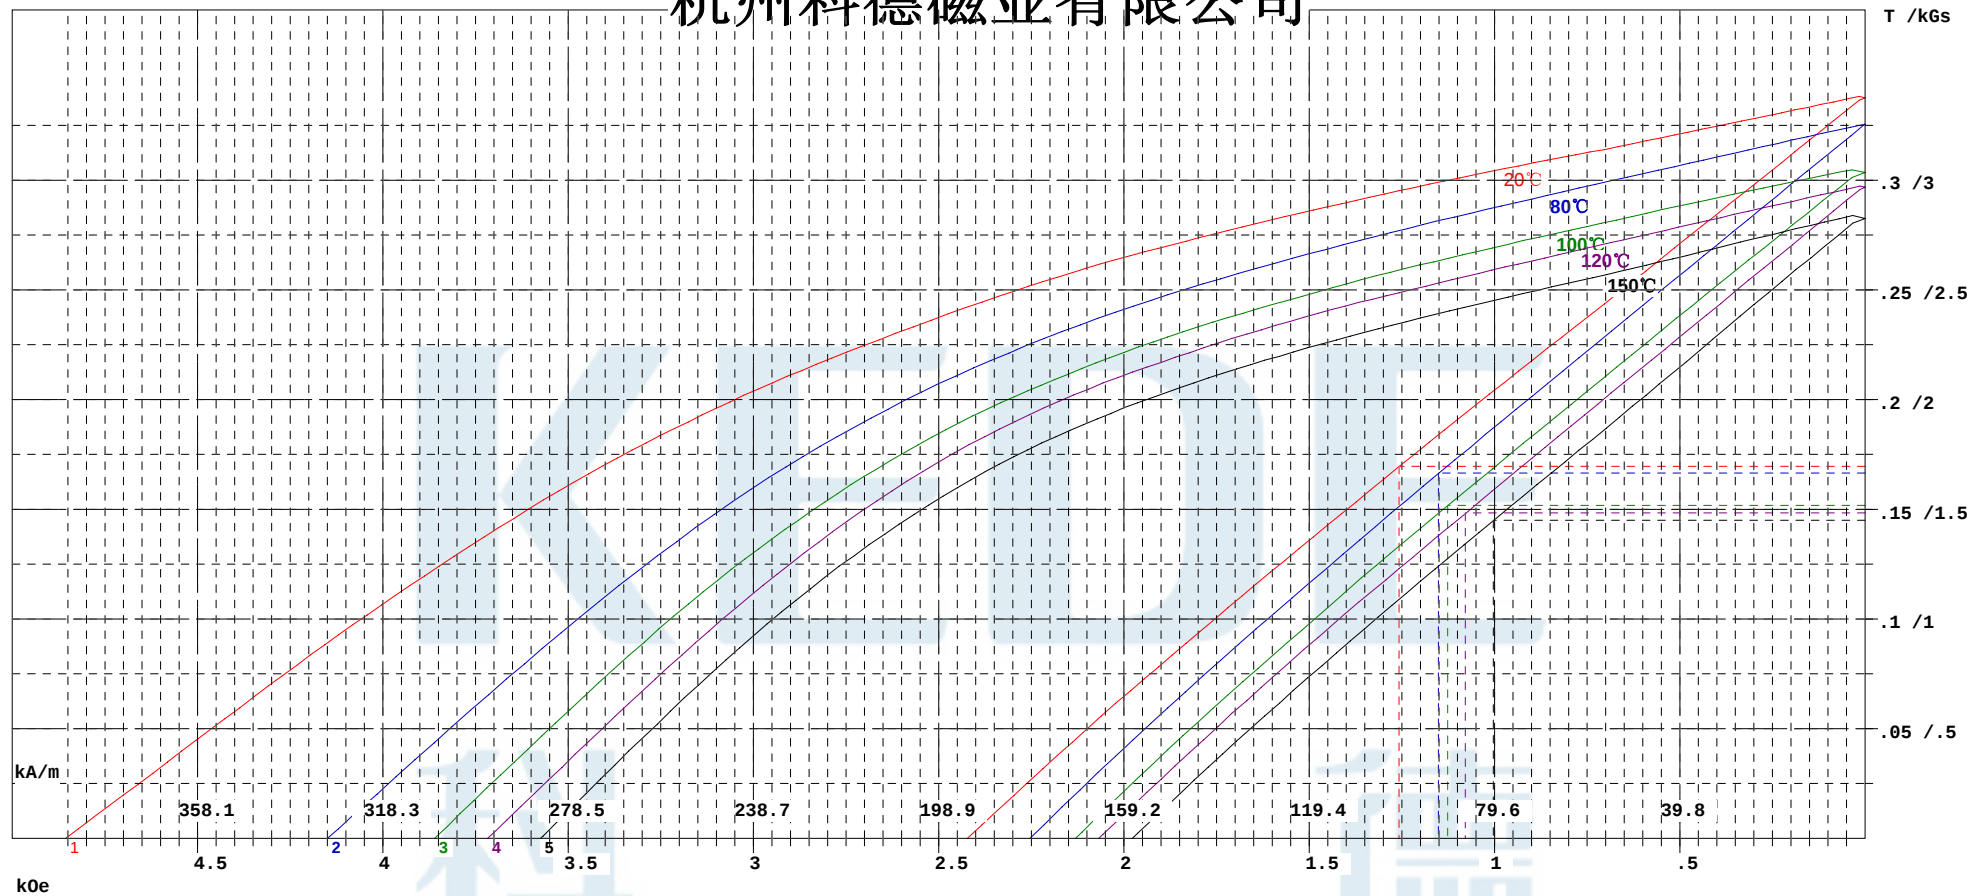

KBI-3

| SampleNo | Br<br>(T) | Hcb<br>(kA/m) | Hcj<br>(kA/m) | (BH)max<br>(kJ/m <sup>3</sup> ) | Hk<br>(kA/m) | Hd<br>(kA/m) | Bd<br>(T) | Hk/Hcj<br>(%) | Test Date | Sample<br>Shape | S-T<br>(°C) | Size<br>(mm) |
|----------|-----------|---------------|---------------|---------------------------------|--------------|--------------|-----------|---------------|-----------|-----------------|-------------|--------------|
|          | 0.339     | 193           | 386           | 17.0                            | 78           | 100          | 0.170     | 20.3          | 2018      | Column          | 20          | 10.00        |
|          | 0.326     | 179           | 330           | 15.3                            | 68           | 92           | 0.167     | 20.7          | 2018      | Column          | 80          | 10.00        |
|          | 0.306     | 170           | 307           | 13.6                            | 67           | 90           | 0.152     | 21.8          | 2018      | Column          | 100         | 10.00        |
|          | 0.298     | 165           | 296           | 12.7                            | 62           | 86           | 0.148     | 20.9          | 2018      | Column          | 120         | 10.00        |
|          | 0.285     | 157           | 284           | 11.6                            | 56           | 80           | 0.145     | 19.7          | 2018      | Column          | 150         | 10.00        |

# 杭州科德磁业有限公司

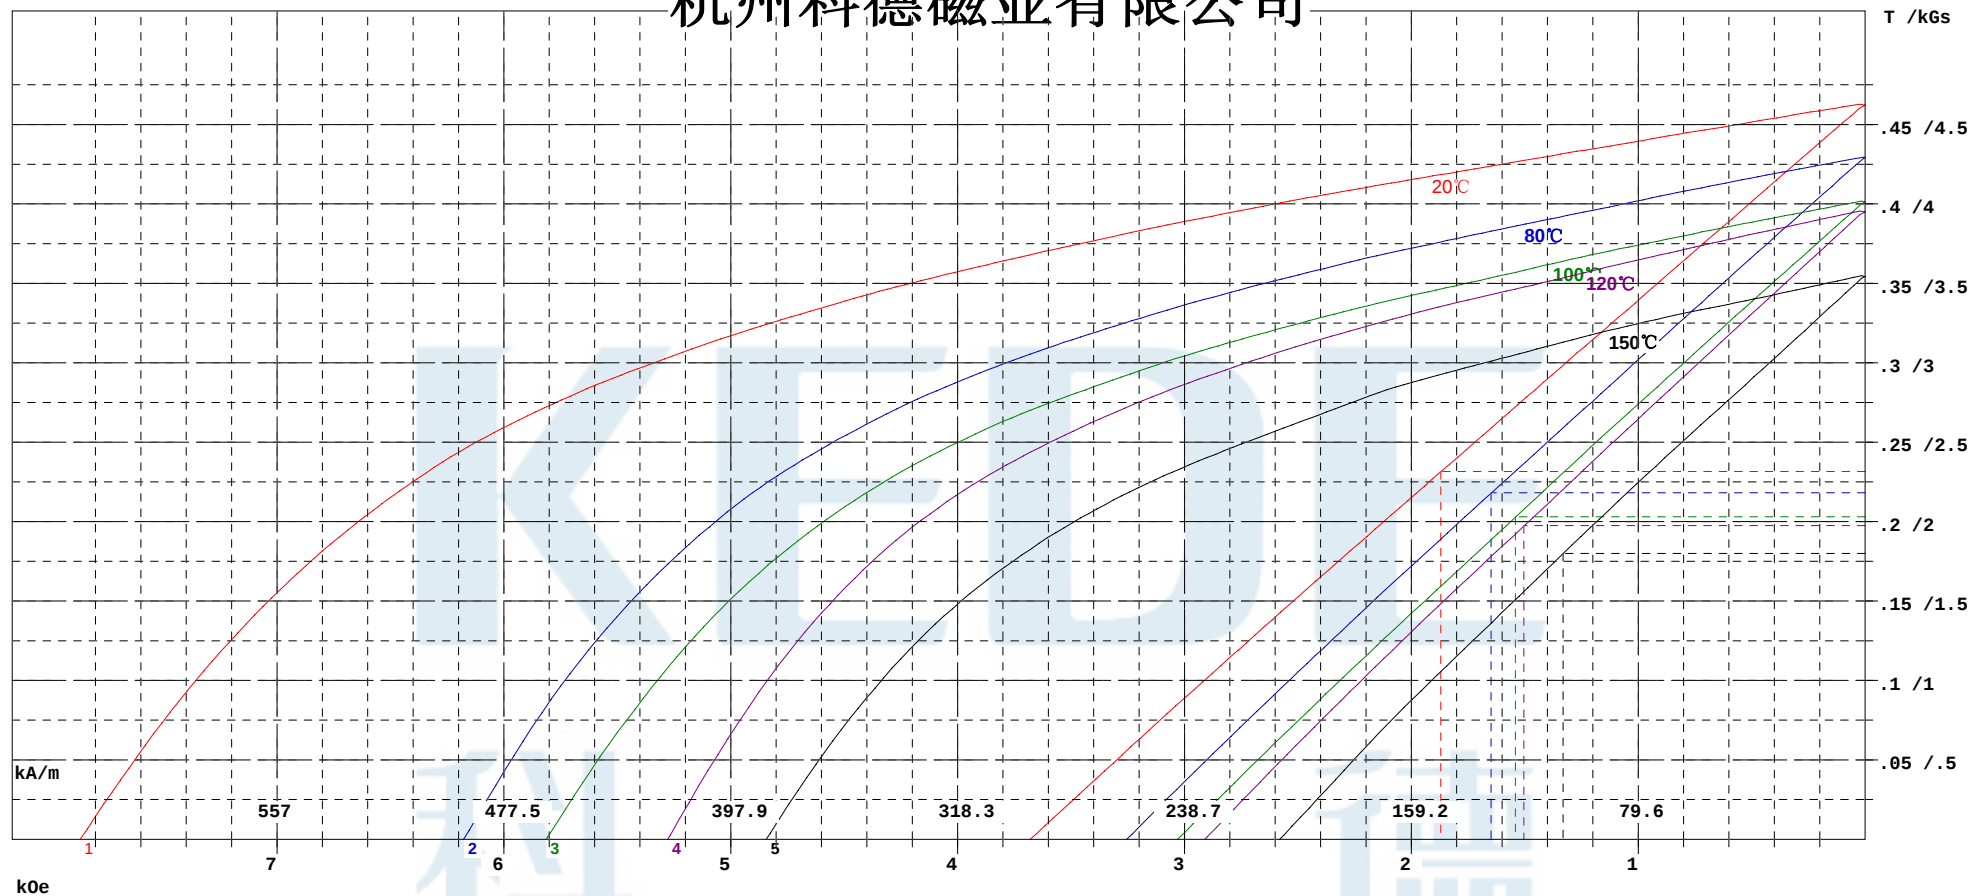


KBI-4

SampleNo


| Br<br>(T) | Hcb<br>(kA/m) | Hcj<br>(kA/m) | (BH)max<br>(kJ/m^3) | Hk<br>(kA/m) | Hd<br>(kA/m) | Bd<br>(T) | Hk/Hcj<br>(%) | Test Date | Sample Shape | S-T<br>(°C) | Size<br>(mm) |
|-----------|---------------|---------------|---------------------|--------------|--------------|-----------|---------------|-----------|--------------|-------------|--------------|
| 0.464     | 293           | 626           | 34.5                | 153          | 149          | 0.232     | 24.5          | 2019      | Column       | 20          | 10.00        |
| 0.430     | 259           | 492           | 28.6                | 121          | 131          | 0.218     | 24.6          | 2019      | Column       | 80          | 10.00        |
| 0.402     | 241           | 463           | 24.9                | 111          | 123          | 0.203     | 24.0          | 2019      | Column       | 100         | 10.00        |
| 0.396     | 232           | 420           | 23.6                | 99           | 120          | 0.197     | 23.6          | 2019      | Column       | 120         | 10.00        |
| 0.355     | 205           | 385           | 19.1                | 91           | 106          | 0.180     | 23.7          | 2019      | Column       | 150         | 10.00        |

# 杭州科德磁业有限公司

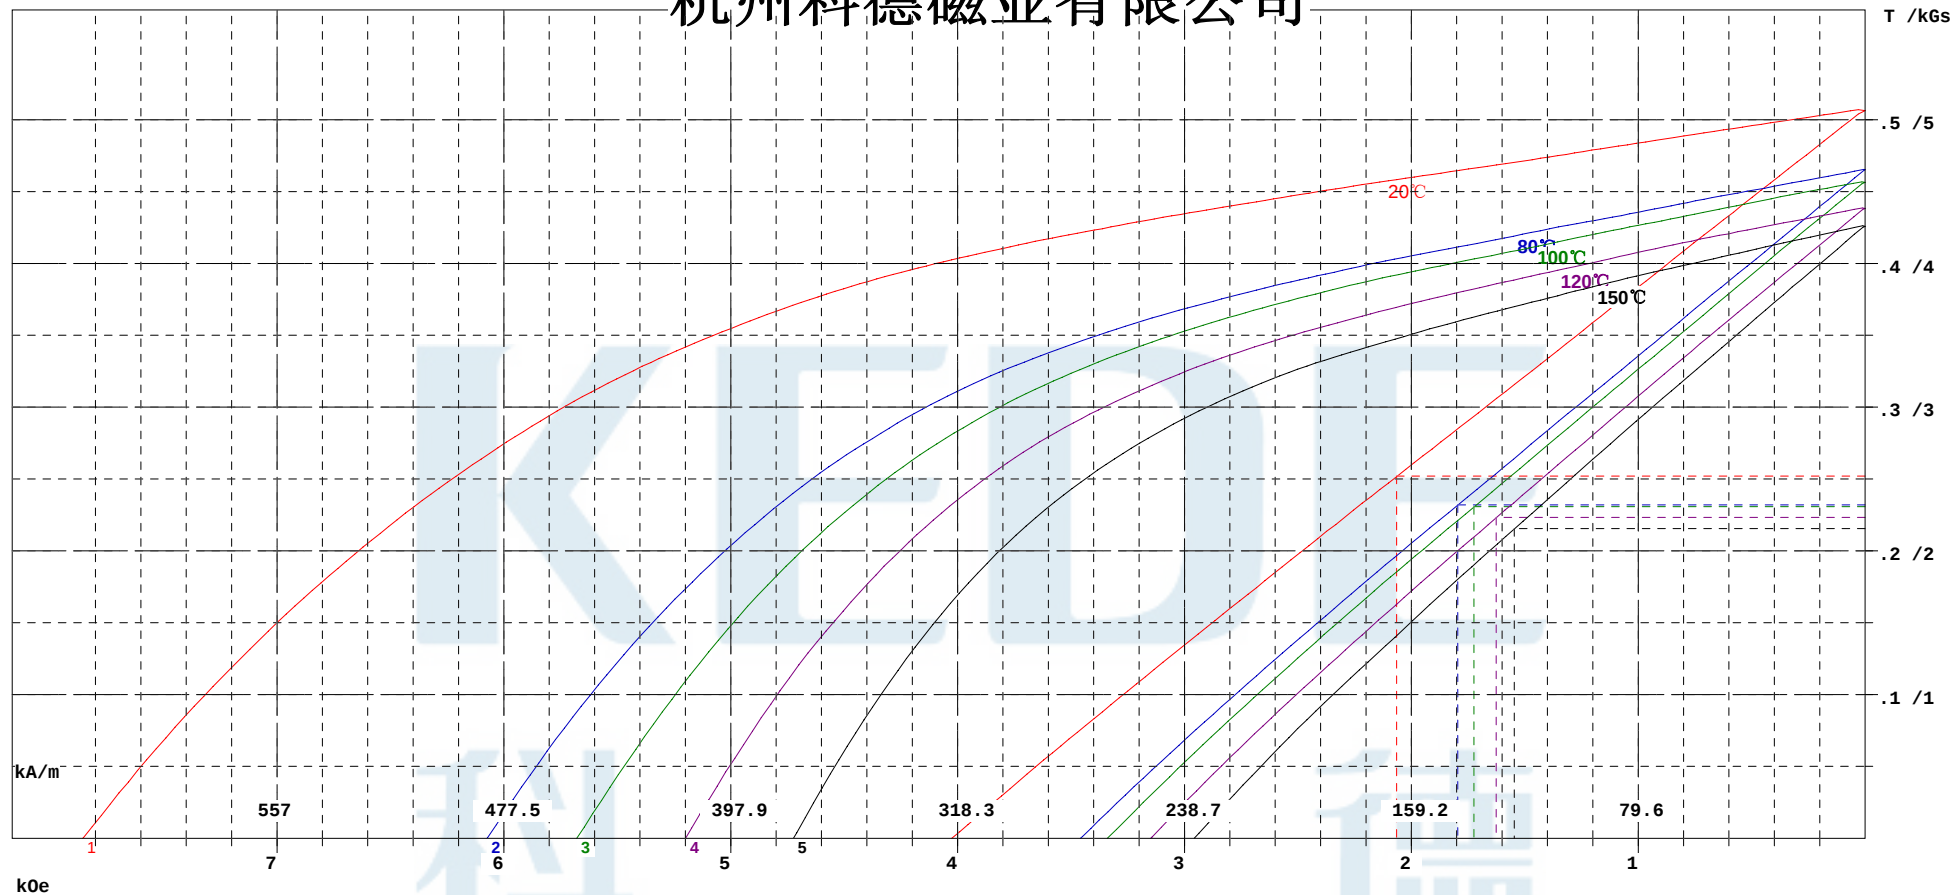

| SampleNo | Br<br>(T) | Hcb<br>(kA/m) | Hcj<br>(kA/m) | (BH)max<br>(kJ/m <sup>3</sup> ) | Hk<br>(kA/m) | Hd<br>(kA/m) | Bd<br>(T) | Hk/Hcj<br>(%) | Test Date | Sample<br>Shape | S-T<br>(°C) | Size<br>(mm) |
|----------|-----------|---------------|---------------|---------------------------------|--------------|--------------|-----------|---------------|-----------|-----------------|-------------|--------------|
| KBI-5    | 0.508     | 320           | 625           | 41.4                            | 169          | 164          | 0.252     | 27.0          | 2019      | Column          | 20          | 10.00        |
|          | 0.466     | 275           | 483           | 33.1                            | 123          | 143          | 0.232     | 25.5          | 2019      | Column          | 80          | 10.00        |
|          | 0.457     | 266           | 452           | 31.7                            | 116          | 137          | 0.231     | 25.7          | 2019      | Column          | 100         | 10.00        |
|          | 0.439     | 251           | 414           | 28.9                            | 108          | 129          | 0.223     | 26.1          | 2019      | Column          | 120         | 10.00        |
|          | 0.427     | 235           | 376           | 26.5                            | 95           | 123          | 0.215     | 25.3          | 2019      | Column          | 150         | 10.00        |

# 杭州科德磁业有限公司

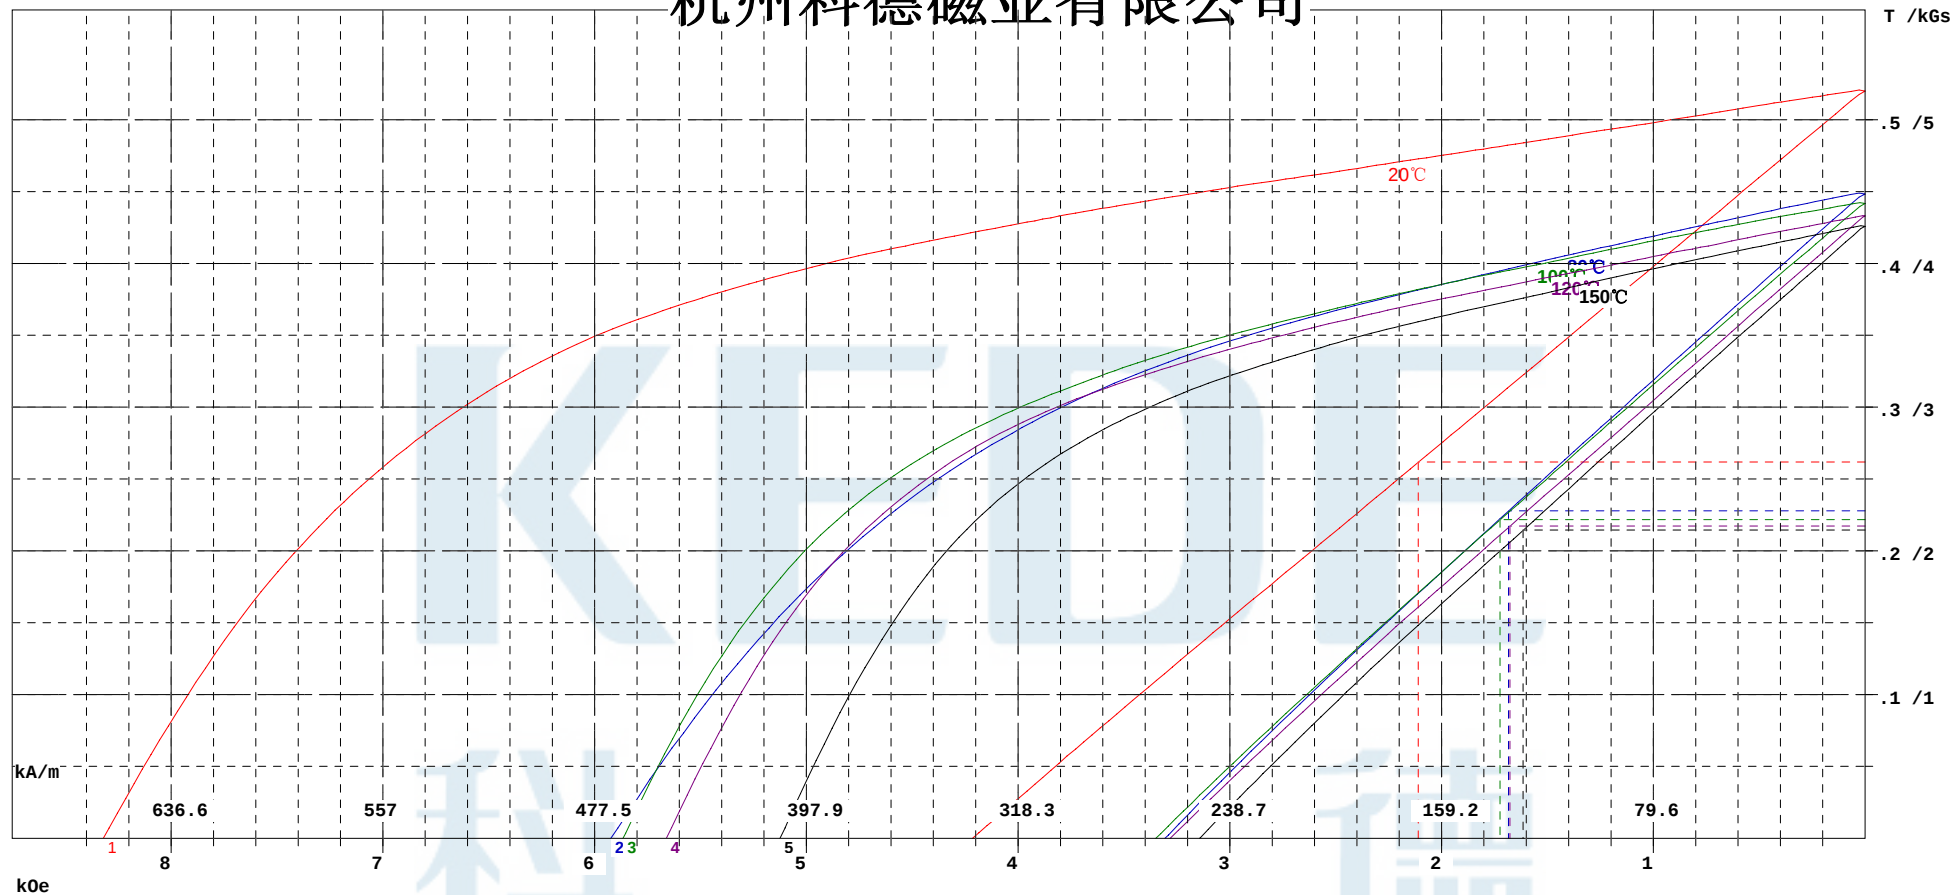


**KBI-5H**

SampleNo


| Br<br>(T) | Hcb<br>(kA/m) | Hcj<br>(kA/m) | (BH)max<br>(kJ/m <sup>3</sup> ) | Hk<br>(kA/m) | Hd<br>(kA/m) | Bd<br>(T) | Hk/Hcj<br>(%) | Test Date | Sample<br>Shape | S-T<br>(°C) | Size<br>(mm) |
|-----------|---------------|---------------|---------------------------------|--------------|--------------|-----------|---------------|-----------|-----------------|-------------|--------------|
| 0.521     | 335           | 662           | 44.0                            | 181          | 168          | 0.262     | 27.3          | 2019      | Column          | 20          | 10.00        |
| 0.450     | 263           | 471           | 30.5                            | 113          | 134          | 0.228     | 24.1          | 2019      | Column          | 80          | 10.00        |
| 0.443     | 267           | 467           | 30.4                            | 125          | 137          | 0.222     | 26.7          | 2019      | Column          | 100         | 10.00        |
| 0.434     | 261           | 450           | 29.0                            | 119          | 133          | 0.217     | 26.5          | 2019      | Column          | 120         | 10.00        |
| 0.427     | 250           | 408           | 27.6                            | 109          | 128          | 0.215     | 26.7          | 2019      | Column          | 150         | 10.00        |

# 杭州科德磁业有限公司

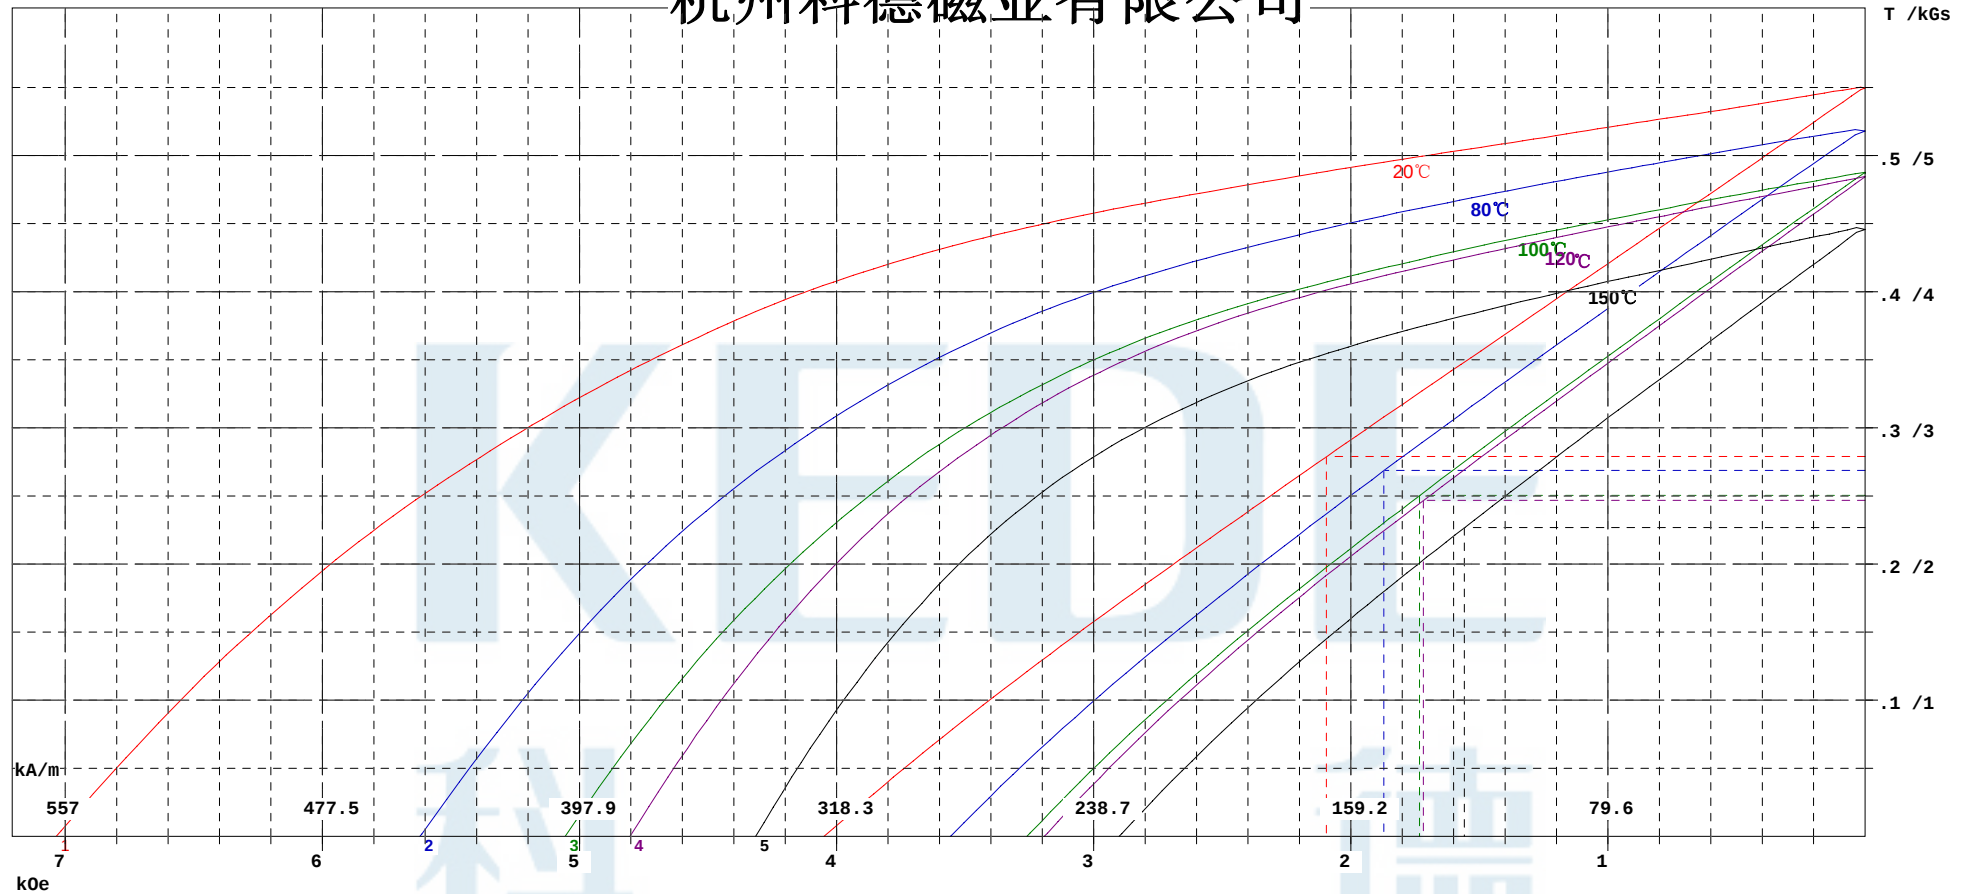

| SampleNo     | Br<br>(T) | Hcb<br>(kA/m) | Hcj<br>(kA/m) | (BH)max<br>(kJ/m <sup>3</sup> ) | Hk<br>(kA/m) | Hd<br>(kA/m) | Bd<br>(T) | Hk/Hcj<br>(%) | Test Date | Sample<br>Shape | S-T<br>(°C) | Size<br>(mm) |
|--------------|-----------|---------------|---------------|---------------------------------|--------------|--------------|-----------|---------------|-----------|-----------------|-------------|--------------|
| <b>KBI-6</b> | 0.551     | 322           | 560           | 46.5                            | 147          | 167          | 0.279     | 26.3          | 2019      | Column          | 20          | 10.00        |
|              | 0.520     | 283           | 447           | 40.0                            | 123          | 149          | 0.269     | 27.5          | 2019      | Column          | 80          | 10.00        |
|              | 0.488     | 259           | 402           | 34.5                            | 109          | 138          | 0.250     | 27.0          | 2019      | Column          | 100         | 10.00        |
|              | 0.485     | 254           | 382           | 33.7                            | 103          | 137          | 0.247     | 26.9          | 2019      | Column          | 120         | 10.00        |
|              | 0.449     | 231           | 343           | 28.1                            | 87           | 124          | 0.227     | 25.3          | 2019      | Column          | 150         | 10.00        |

# 杭州科德磁业有限公司

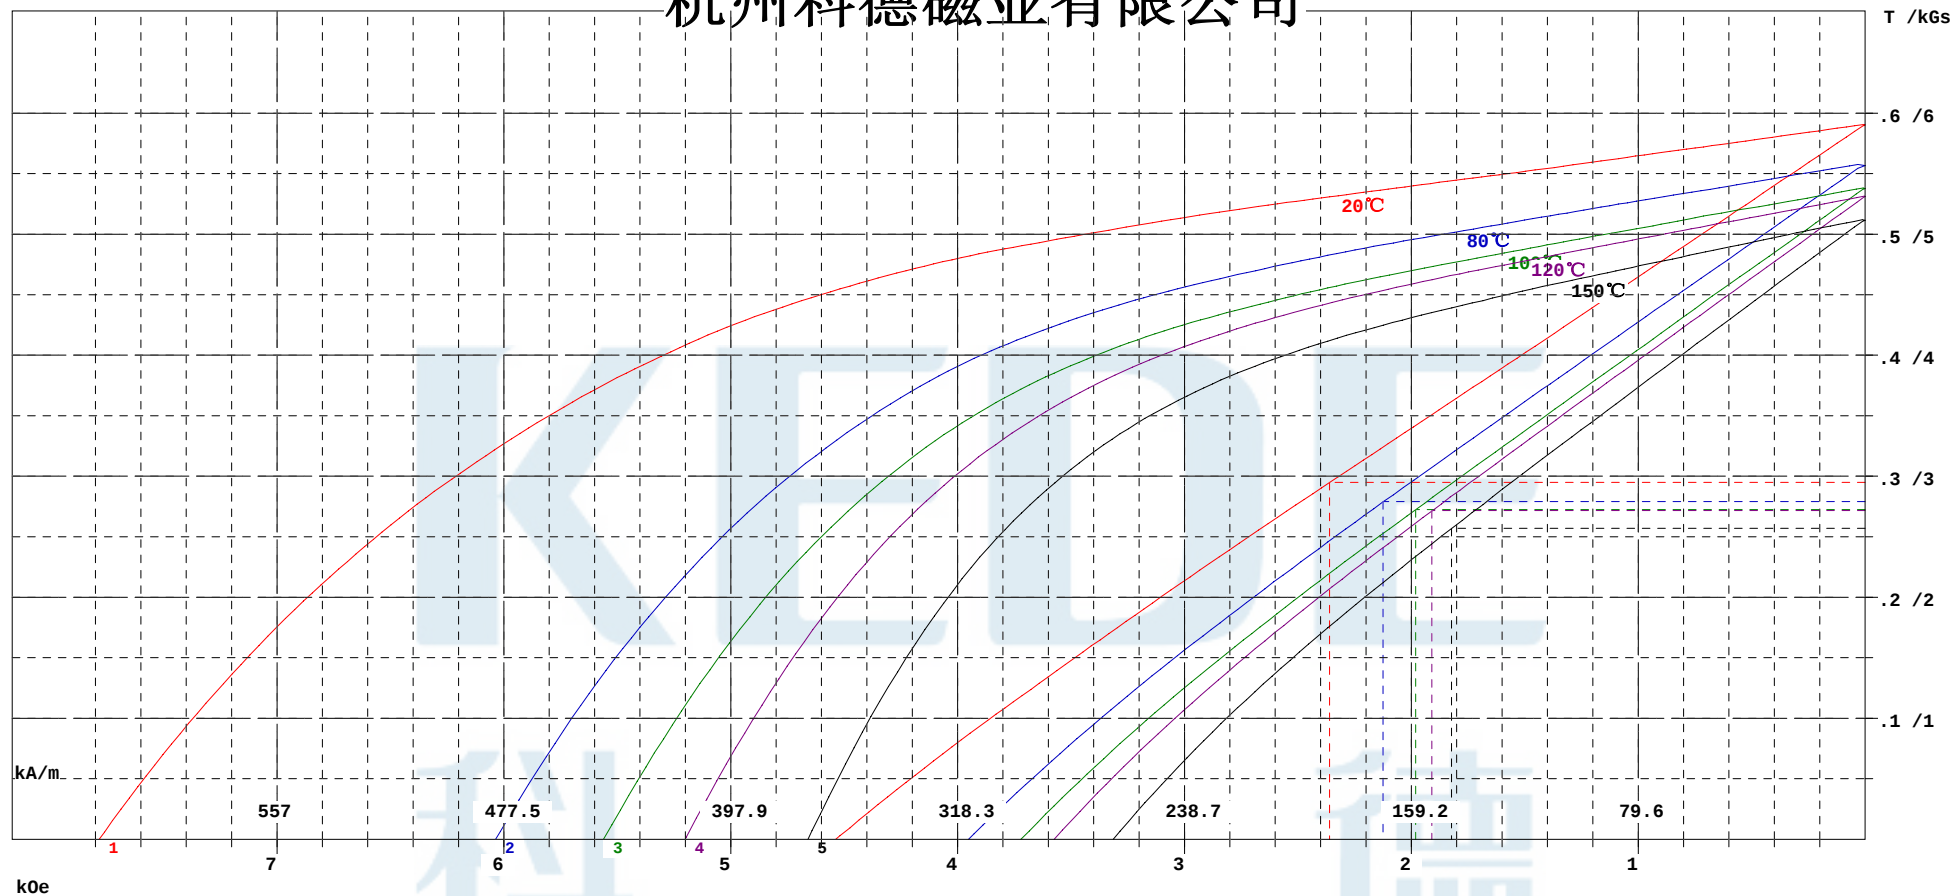


**KBI-7**

SampleNo

| Br<br>(T) | Hcb<br>(kA/m) | Hcj<br>(kA/m) | (BH)max<br>(kJ/m³) | Hk<br>(kA/m) | Hd<br>(kA/m) | Bd<br>(T) | Hk/Hcj<br>(%) | Test Date | Sample<br>Shape | S-T<br>(°C) | Size<br>(mm) |
|-----------|---------------|---------------|--------------------|--------------|--------------|-----------|---------------|-----------|-----------------|-------------|--------------|
| 0.591     | 361           | 619           | 55.4               | 185          | 188          | 0.295     | 29.9          | 2019      | Column          | 20          | 10.00        |
| 0.559     | 315           | 480           | 47.2               | 141          | 169          | 0.279     | 29.4          | 2019      | Column          | 80          | 10.00        |
| 0.538     | 296           | 443           | 43.0               | 127          | 158          | 0.272     | 28.6          | 2019      | Column          | 100         | 10.00        |
| 0.532     | 284           | 414           | 41.3               | 118          | 152          | 0.272     | 28.6          | 2019      | Column          | 120         | 10.00        |
| 0.513     | 264           | 371           | 37.3               | 104          | 145          | 0.257     | 28.1          | 2019      | Column          | 150         | 10.00        |

# 杭州科德磁业有限公司

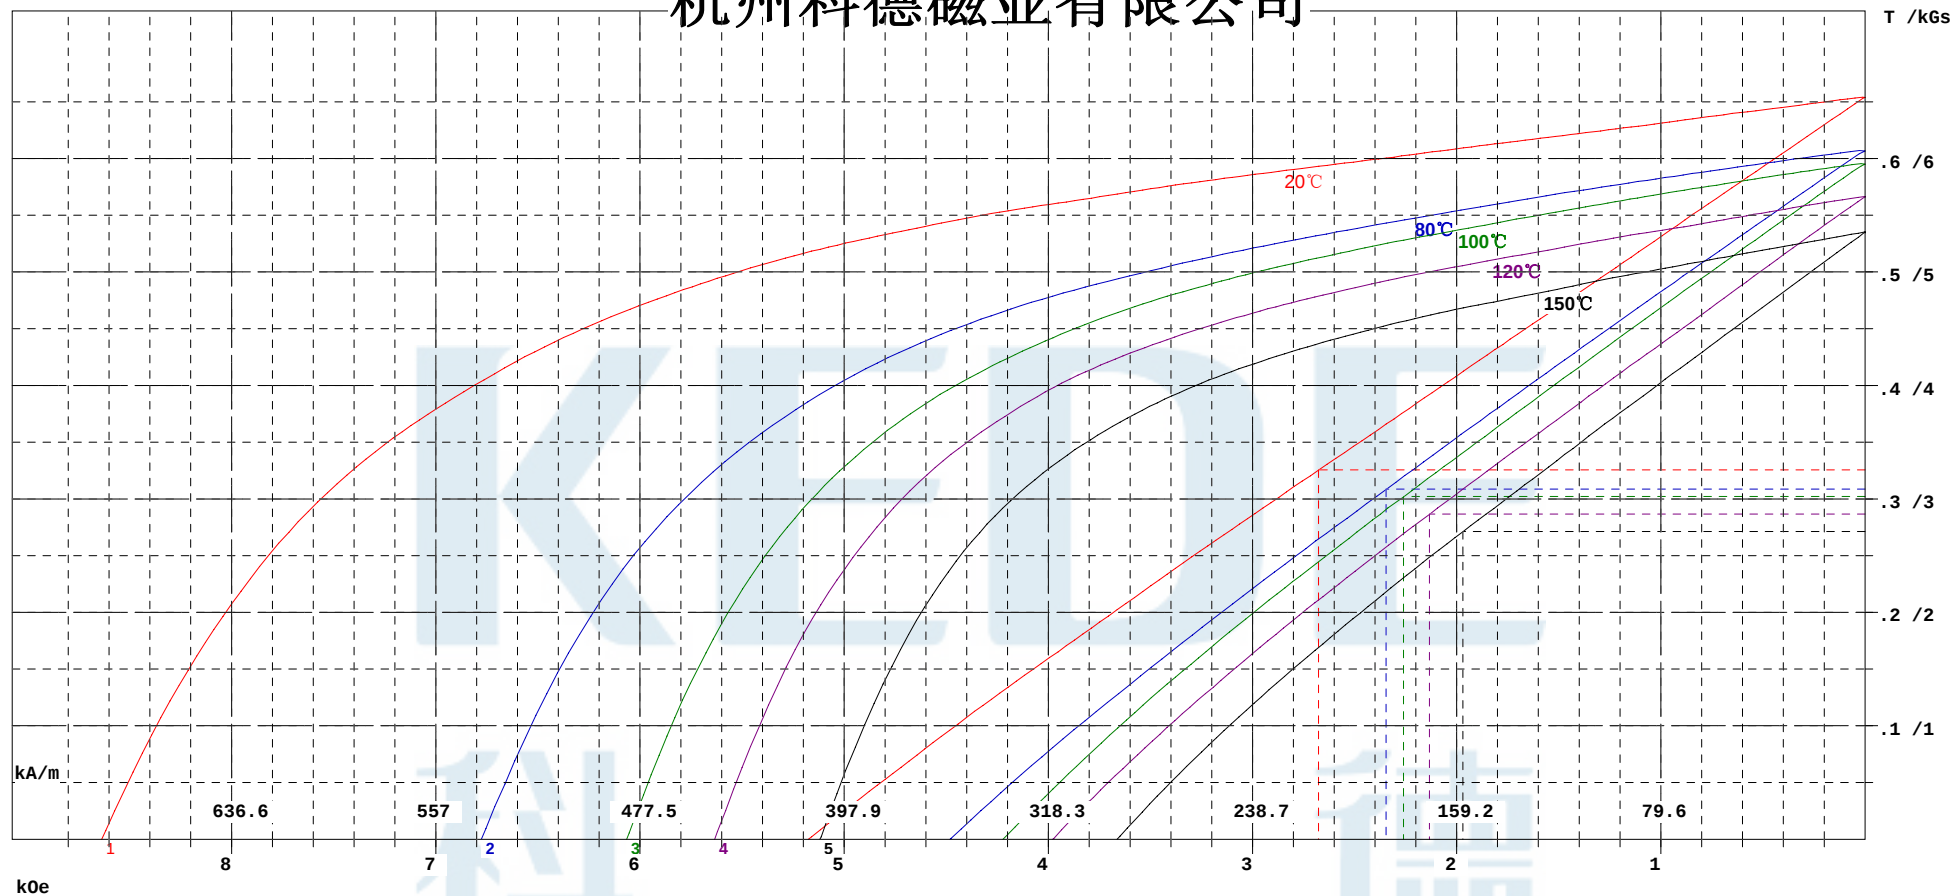

KBI-8

| Br<br>(T) | Hcb<br>(kA/m) | Hcj<br>(kA/m) | (BH)max<br>(kJ/m^3) | Hk<br>(kA/m) | Hd<br>(kA/m) | Bd<br>(T) | Hk/Hcj<br>(%) | Test Date | Sample<br>Shape | S-T<br>(°C) | Size<br>(mm) |
|-----------|---------------|---------------|---------------------|--------------|--------------|-----------|---------------|-----------|-----------------|-------------|--------------|
| 0.655     | 412           | 687           | 69.3                | 228          | 213          | 0.326     | 33.1          | 2019      | Column          | 20          | 10.00        |
| 0.608     | 357           | 539           | 57.6                | 177          | 187          | 0.309     | 32.8          | 2019      | Column          | 80          | 10.00        |
| 0.596     | 336           | 483           | 54.4                | 160          | 180          | 0.302     | 33.2          | 2019      | Column          | 100         | 10.00        |
| 0.567     | 317           | 448           | 48.7                | 147          | 170          | 0.287     | 32.7          | 2019      | Column          | 120         | 10.00        |
| 0.535     | 292           | 407           | 42.5                | 127          | 157          | 0.271     | 31.1          | 2019      | Column          | 150         | 10.00        |