



杭州科德磁业有限公司

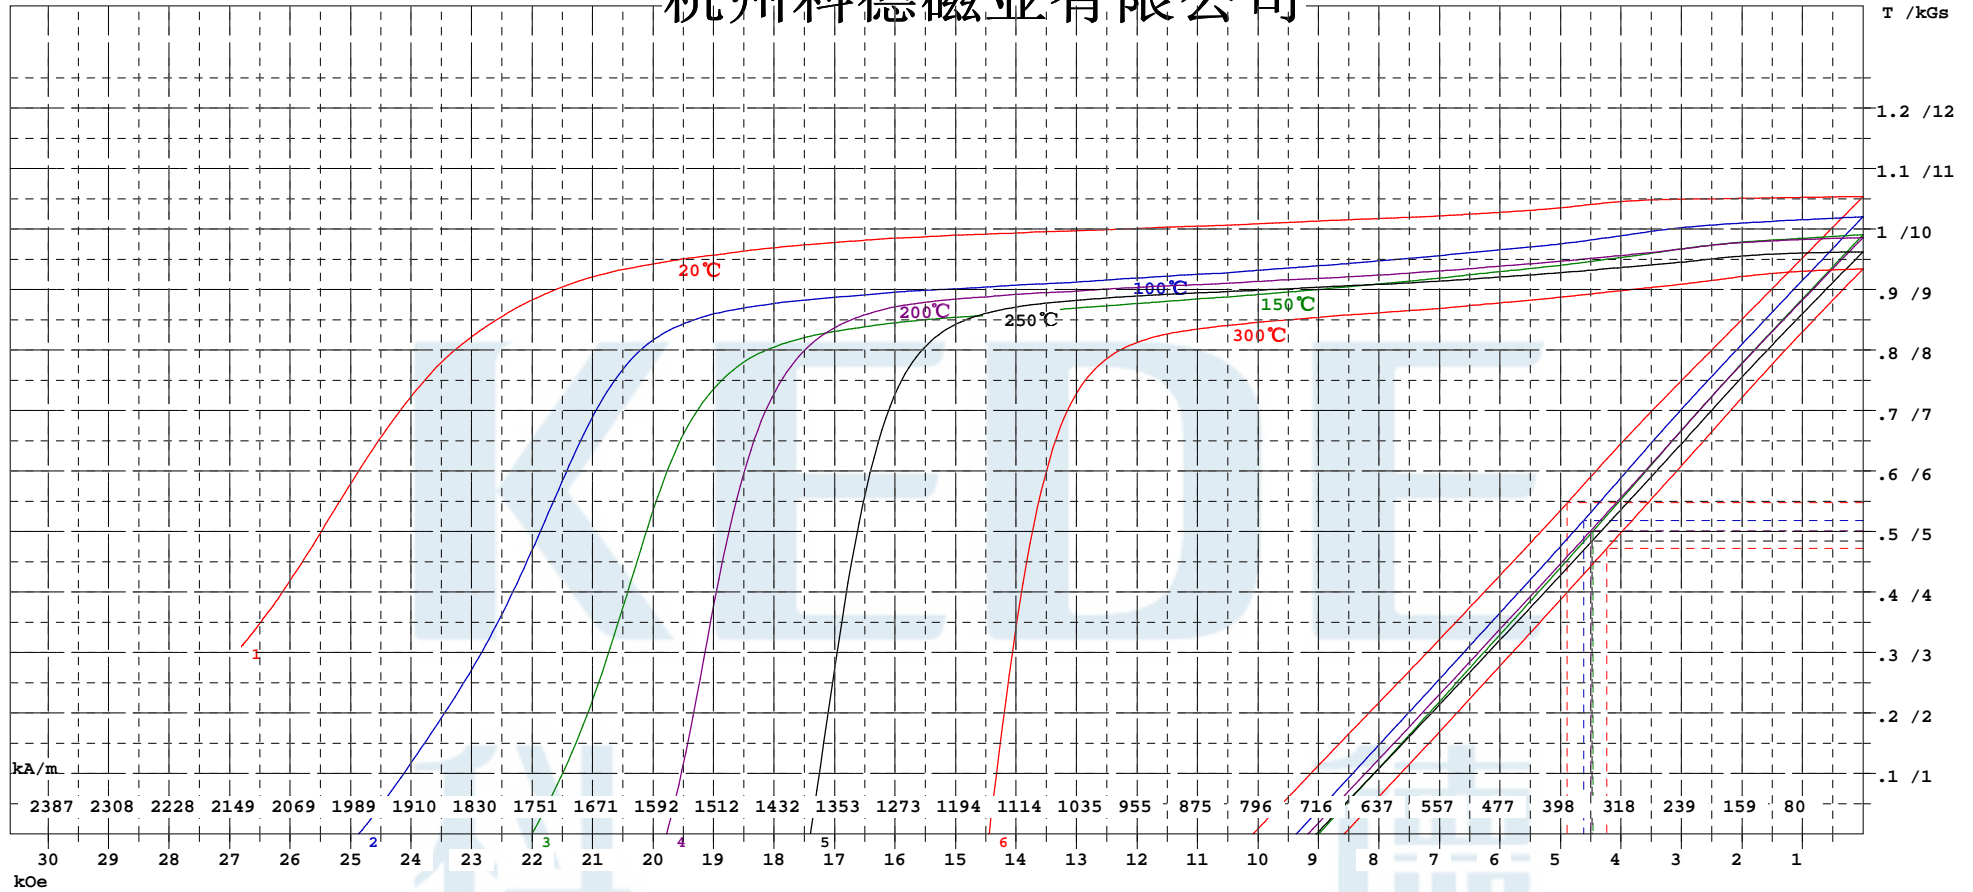

SampleNo	Br (kGs)	Hcb (kOe)	Hcj (kOe)	(BH) _{max} (MGOe)	Hk (kOe)	Hd (kOe)	Bd	Hk/Hcj (%)	Test Date	Sample Shape	S-T (°C)	Size (mm)
1	10.54	10.08	>26.79	26.77	19.66	4.89	5.48	<73.4	2018	Column	20	10.00
2	10.20	9.37	24.87	23.94	12.13	4.62	5.18	48.8	2018	Column	100	10.00
3	9.91	9.00	22.00	22.34	10.02	4.46	5.00	45.5	2018	Column	150	10.00
4	9.86	9.18	19.78	22.57	14.60	4.50	5.01	73.8	2018	Column	200	10.00
5	9.62	9.04	17.40	21.69	14.27	4.48	4.84	82.0	2018	Column	250	10.00
6	9.34	8.58	14.45	20.00	10.49	4.24	4.72	72.6	2018	Column	300	10.00

Sm₂Co₁₇-26H


杭州科德磁业有限公司

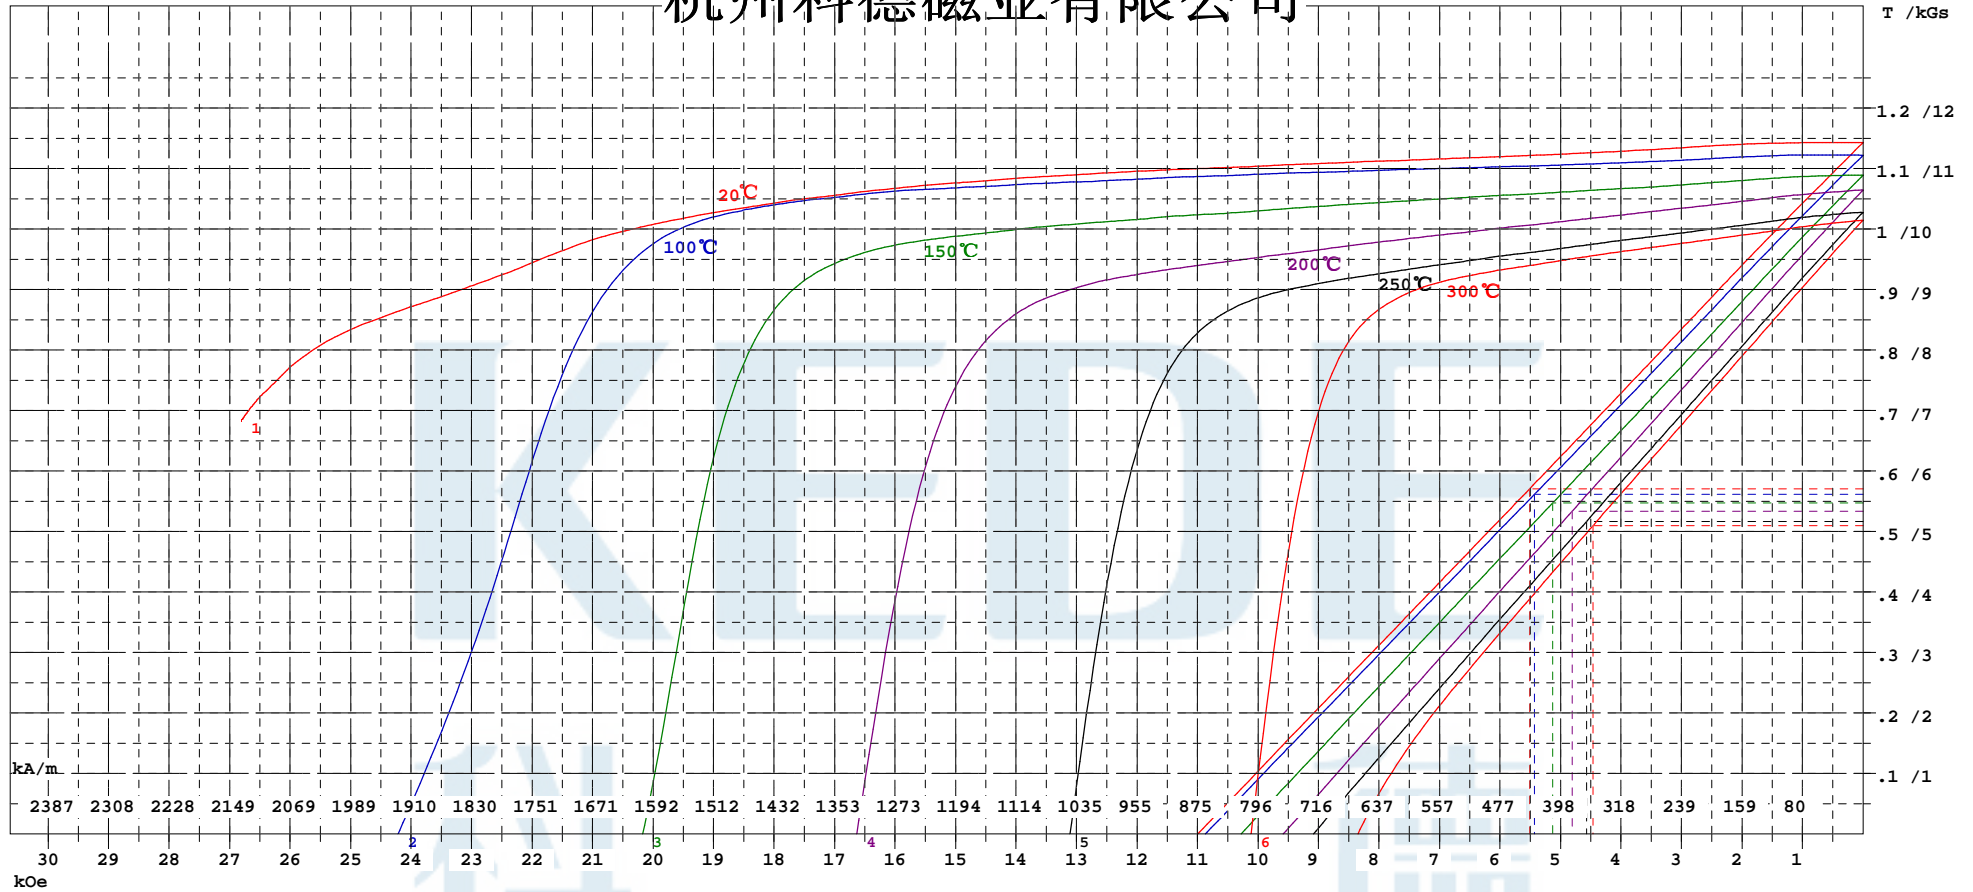

SampleNo	Br (kGs)	Hcb (kOe)	Hcj (kOe)	(BH)max (MGOe)	Hk (kOe)	Hd (kOe)	Bd (kGs)	Hk/Hcj (%)	Test Date	Sample Shape	S-T (°C)	Size (mm)
1	11.43	11.00	>26.80	31.45	18.91	5.51	5.71	<70.6	2018	Column	20	10.00
2	11.22	10.87	24.22	30.49	19.33	5.43	5.62	79.8	2018	Column	100	10.00
3	10.89	10.28	20.17	28.07	15.59	5.13	5.47	77.3	2018	Column	150	10.00
4	10.65	9.58	16.63	25.66	9.59	4.81	5.34	57.6	2018	Column	200	10.00
5	10.28	9.08	13.11	23.61	8.08	4.57	5.17	61.6	2018	Column	250	10.00
6	10.15	8.35	10.11	22.76	6.96	4.46	5.10	68.8	2018	Column	300	10.00

Sm2Co17-33H


杭州科德磁业有限公司

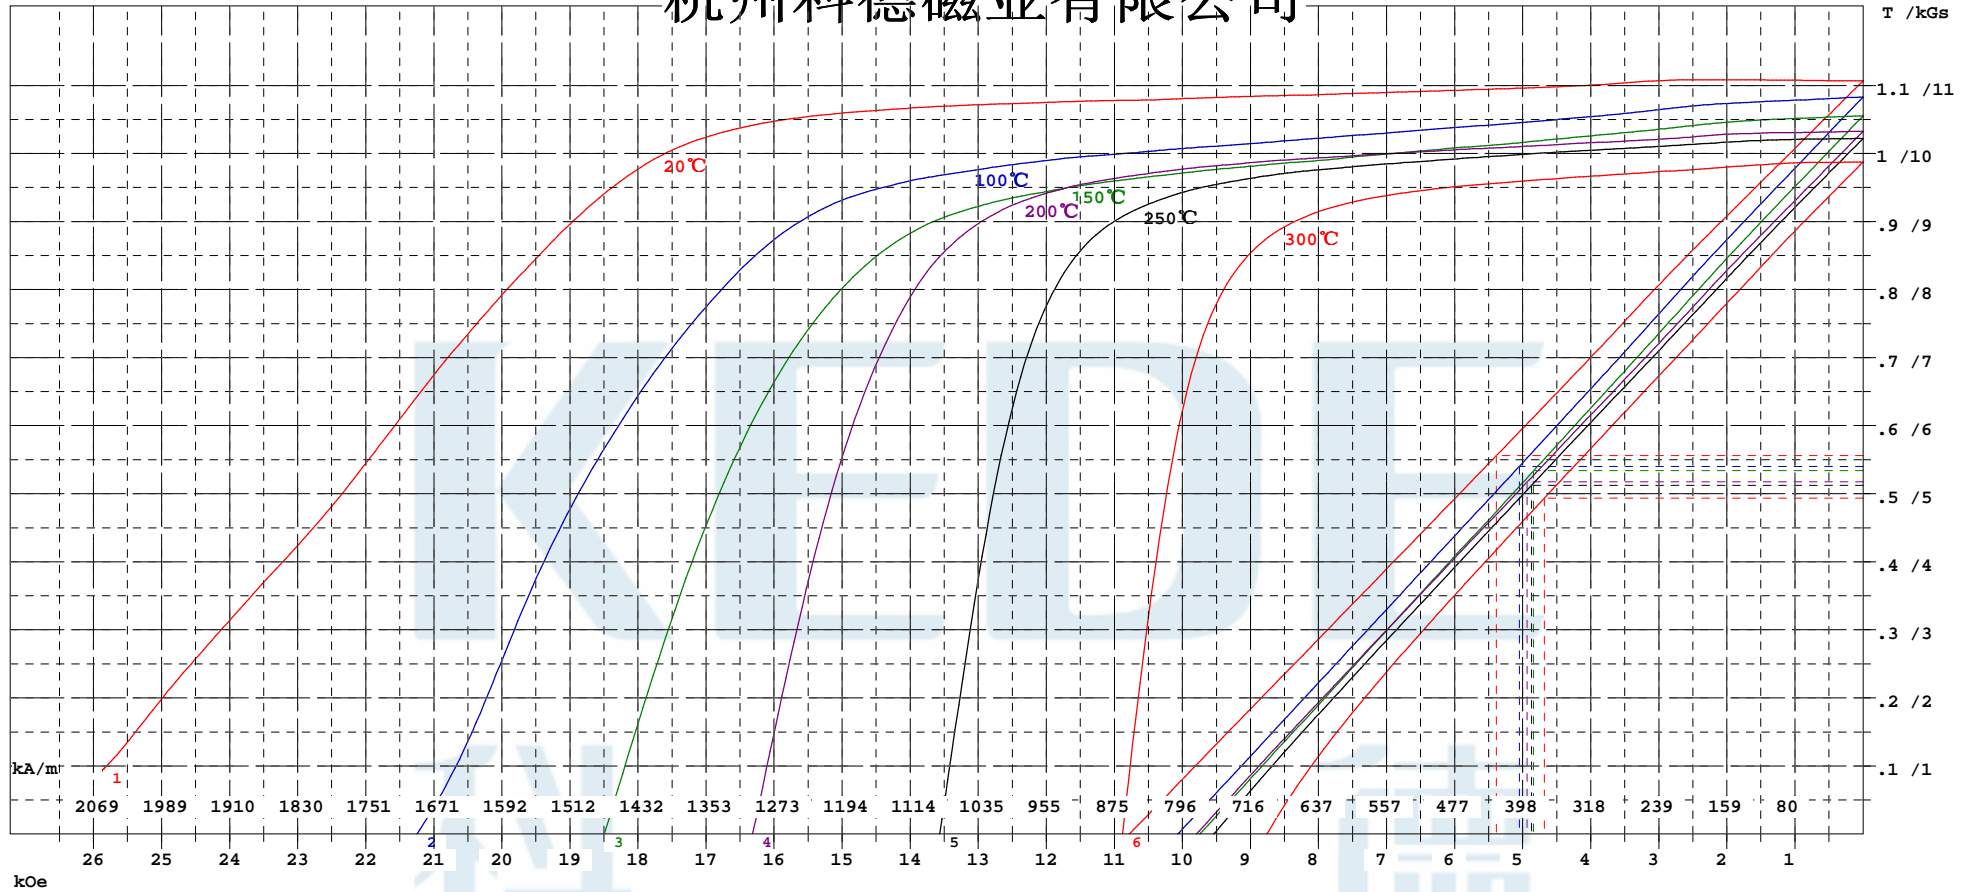

SampleNo	Br (kGs)	Hcb (kOe)	Hcj (kOe)	(BH) _{max} (MGOe)	Hk (kOe)	Hd (kOe)	Bd (kGs)	Hk/Hcj (%)	Test Date	Sample Shape	S-T (°C)	Size (mm)
1	11.07	10.78	>25.86	29.96	17.68	5.39	5.56	<68.4	2018	Column	20	10.00
2	10.83	10.07	21.25	27.29	13.11	5.05	5.40	61.7	2018	Column	100	10.00
3	10.55	9.74	18.50	25.84	11.69	4.84	5.34	63.2	2018	Column	150	10.00
4	10.32	9.79	16.32	25.53	12.38	4.94	5.17	75.9	2018	Column	200	10.00
5	10.22	9.54	13.57	24.96	10.64	4.87	5.13	78.4	2018	Column	250	10.00
6	9.88	8.76	10.88	23.11	8.56	4.68	4.94	78.7	2018	Column	300	10.00


Sm₂Co₁₇-32H

杭州科德磁业有限公司

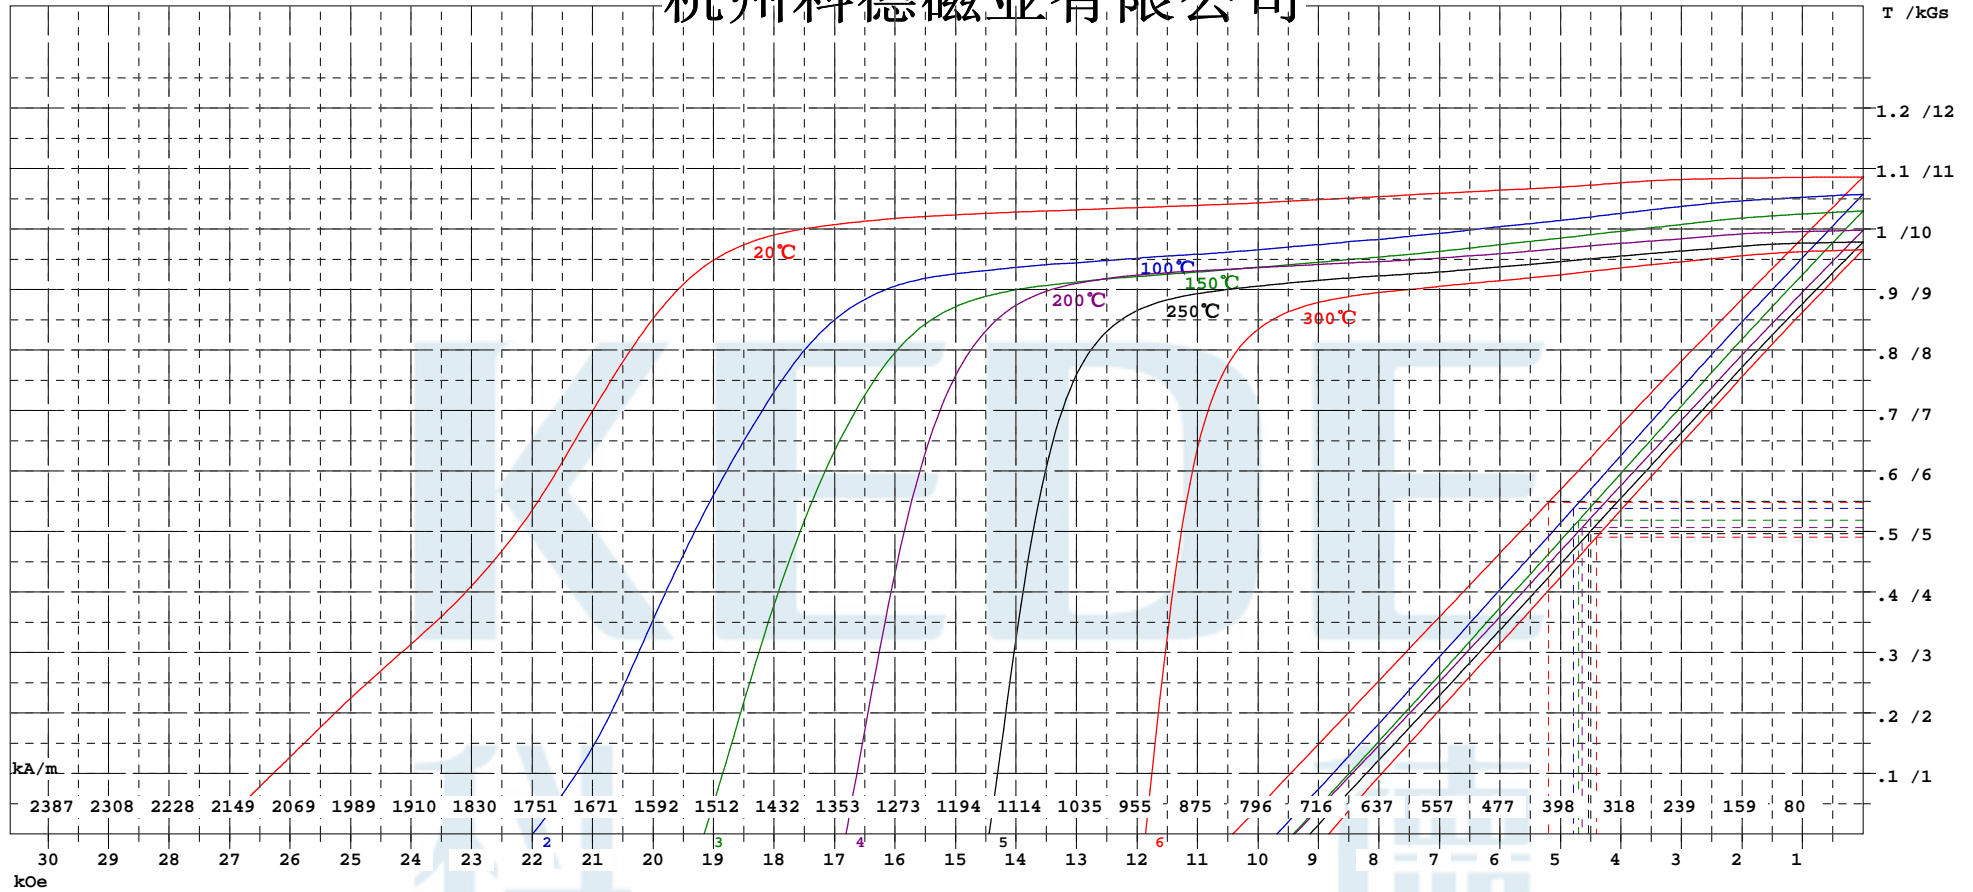


SampleNo	Br (kGs)	Hcb (kOe)	Hcj (kOe)	(BH) _{max} (MGOe)	Hk (kOe)	Hd (kOe)	Bd (kGs)	Hk/Hcj (%)	Test Date	Sample Shape	S-T (°C)	Size (mm)
Sm2Co17-28H	10.86	10.41	>26.78	28.51	18.41	5.20	5.48	<68.8	2018	Column	20	10.00
Sm2Co17-28H	10.58	9.68	21.99	25.76	12.01	4.78	5.38	54.6	2018	Column	100	10.00
Sm2Co17-28H	10.30	9.42	19.16	24.37	11.27	4.70	5.19	58.8	2018	Column	150	10.00
Sm2Co17-28H	9.98	9.39	16.81	23.54	13.48	4.64	5.07	80.1	2018	Column	200	10.00
Sm2Co17-28H	9.79	9.14	14.45	22.55	11.59	4.54	4.97	80.2	2018	Column	250	10.00
Sm2Co17-28H	9.66	8.83	11.86	21.62	9.34	4.41	4.91	78.7	2018	Column	300	10.00

杭州科德磁业有限公司

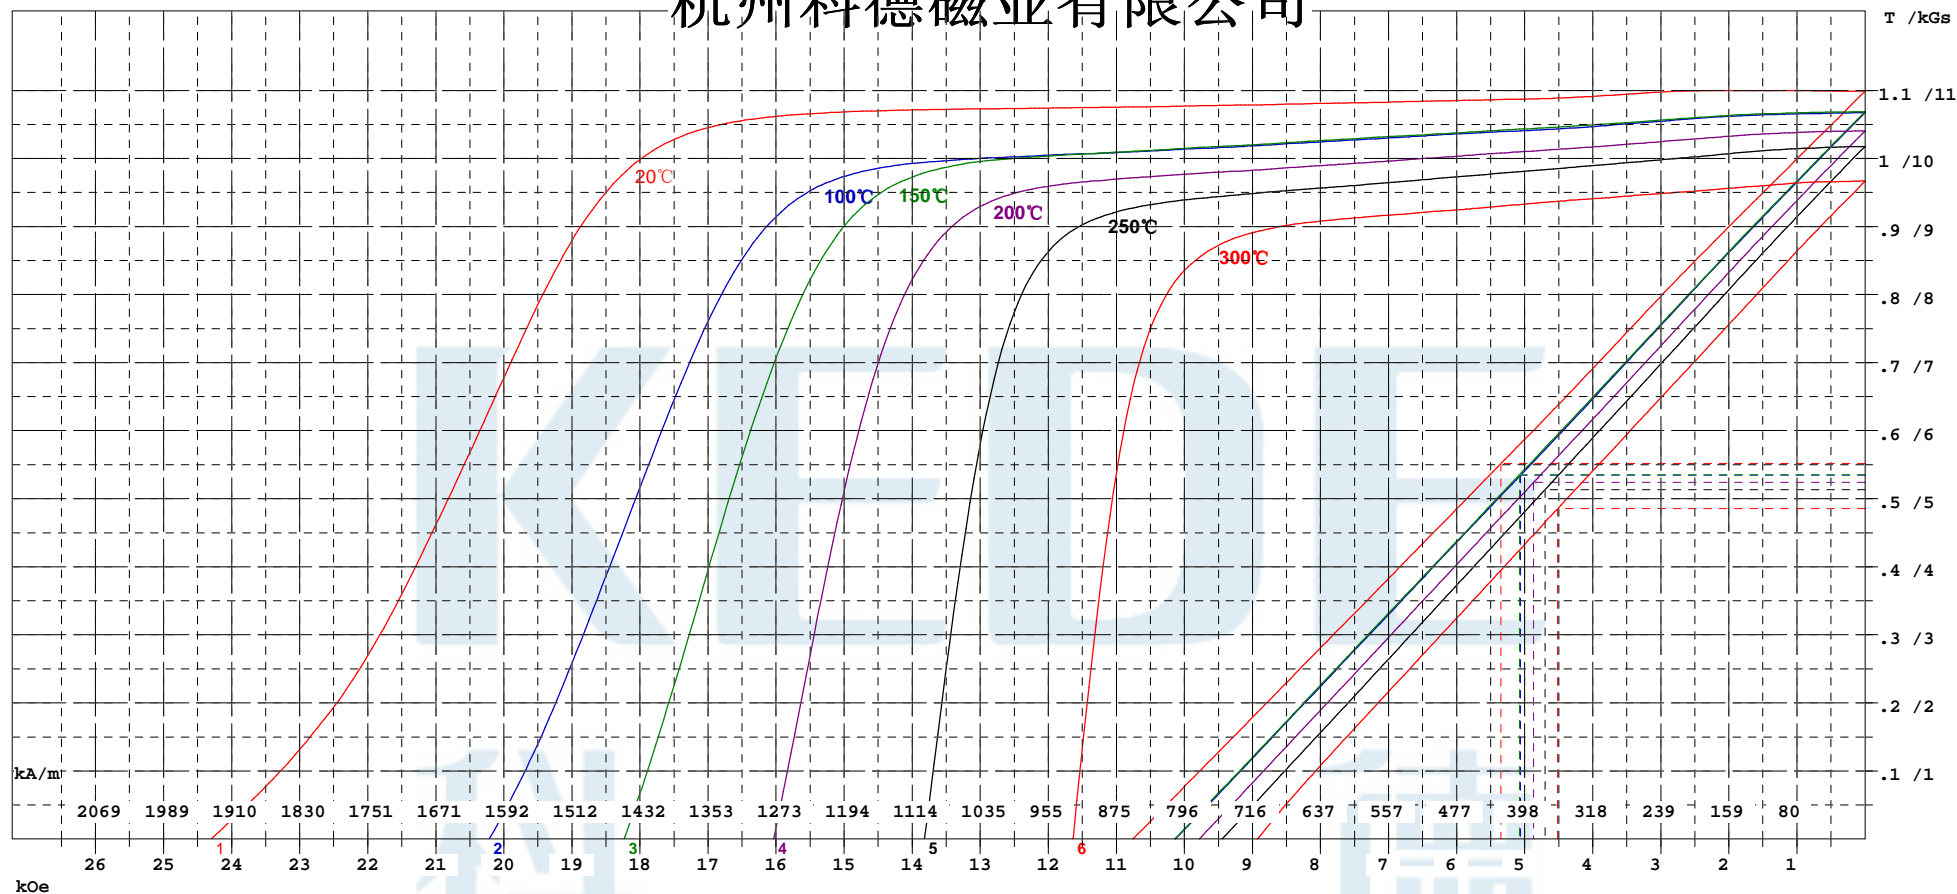

SampleNo	Br (kGs)	Hcb (kOe)	Hcj (kOe)	(BH) _{max} (MGOe)	Hk (kOe)	Hd (kOe)	Bd (kGs)	Hk/Hcj (%)	Test Date	Sample Shape	S-T (°C)	Size (mm)
1	10.99	10.76	24.30	29.52	18.12	5.35	5.52	74.6	2018	Column 20	20	10.00
2	10.67	10.13	20.22	27.05	15.35	5.06	5.34	75.9	2018	Column 100	100	10.00
3	10.69	10.14	18.23	27.19	14.25	5.08	5.35	78.2	2018	Column 150	150	10.00
4	10.41	9.78	16.03	25.52	12.86	4.87	5.24	80.2	2018	Column 200	200	10.00
5	10.18	9.45	13.82	24.14	11.17	4.70	5.13	80.9	2018	Column 250	250	10.00
6	9.67	8.93	11.64	21.93	9.54	4.52	4.86	82.0	2018	Column 300	300	10.00

杭州科德磁业有限公司

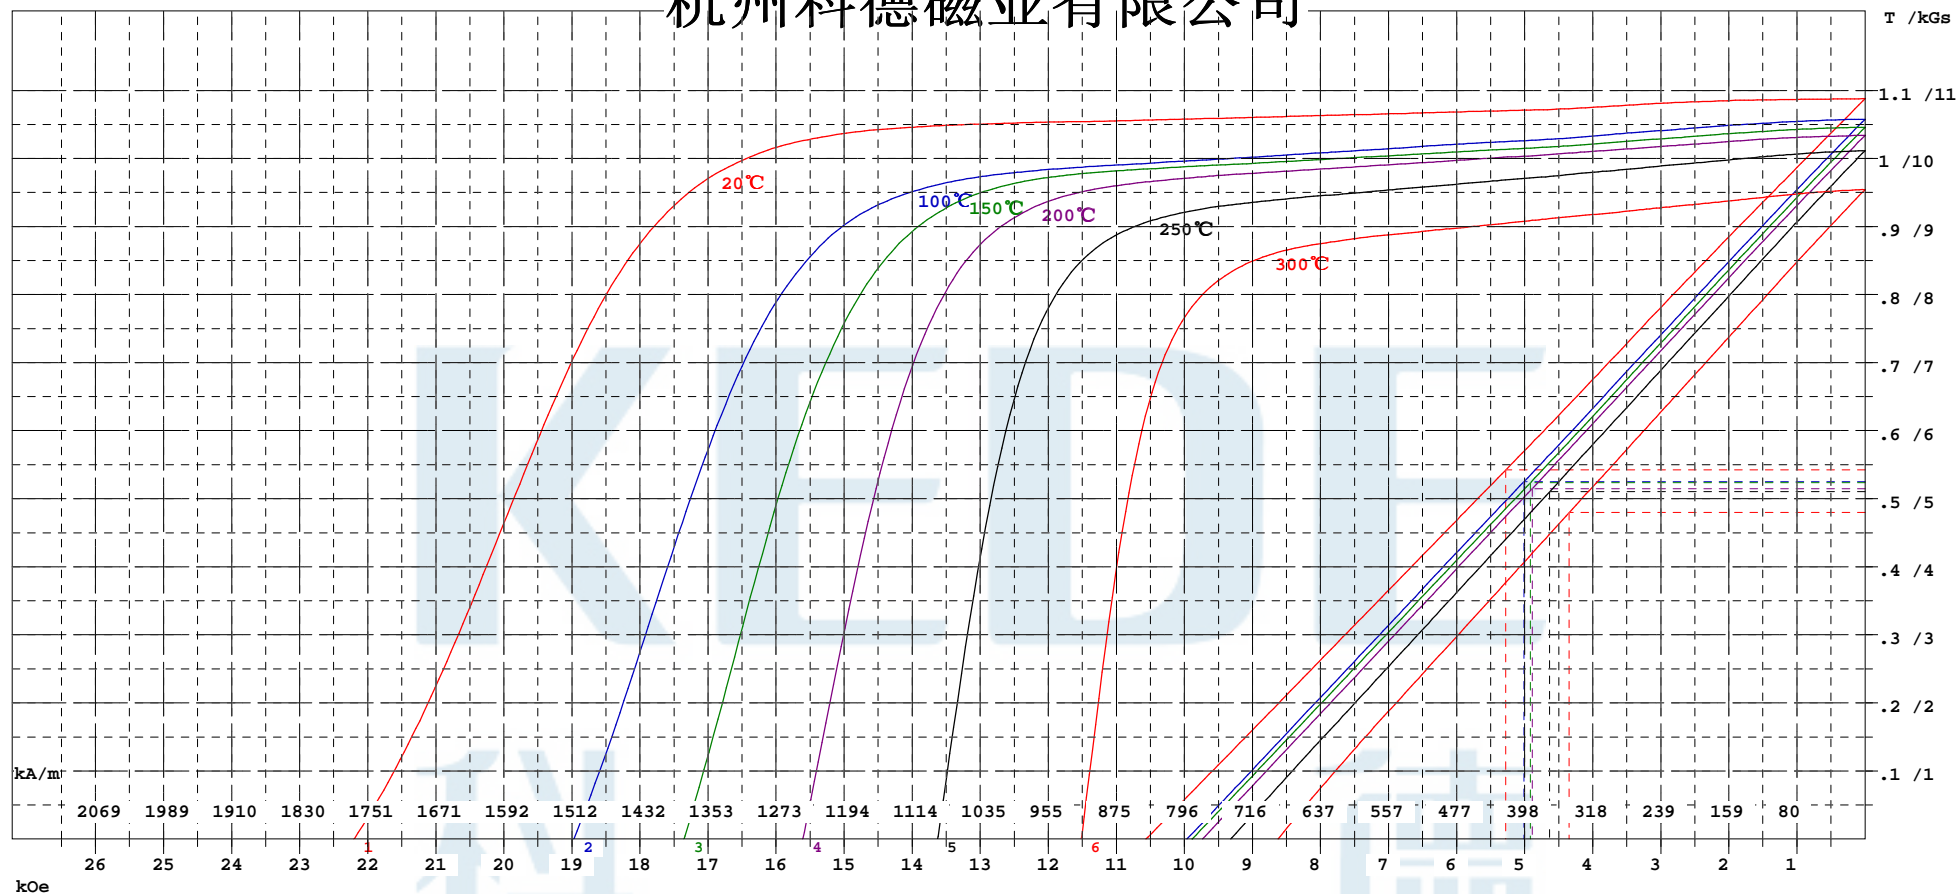

SampleNo	Br (kGs)	Hcb (kOe)	Hcj (kOe)	(BH) _{max} (MGOe)	Hk (kOe)	Hd (kOe)	Bd (kGs)	Hk/Hcj (%)	Test Date	Sample Shape	S-T (°C)	Size (mm)
1	10.88	10.56	22.20	28.63	16.86	5.28	5.43	75.9	2018	Column	20	10.00
2	10.58	9.96	18.97	26.31	13.97	5.01	5.25	73.6	2018	Column	100	10.00
3	10.46	9.89	17.35	25.74	13.22	4.92	5.24	76.2	2018	Column	150	10.00
4	10.34	9.73	15.61	25.19	12.16	4.89	5.15	77.9	2018	Column	200	10.00
5	10.12	9.32	13.63	23.65	10.43	4.63	5.10	76.6	2018	Column	250	10.00
6	9.55	8.62	11.51	20.86	8.73	4.35	4.80	75.8	2018	Column	300	10.00

Sm₂Co₁₇-30